

Fig. 4  
Infrared camera image of single fiber (left) and nonwoven fiber mat (right)



lines. Up to 3.5 wt% of CNT, spinning parameters can be varied in the same range compared to the neat material. For higher concentrations, only lower melt draw ratios are possible because of the viscosity increase caused by CNT [6].

#### Electrical conductivity

After the extrusion of the fibers, electrical conductivity is checked to find the percolation threshold, defined by the CNT concentration, where the specific resistivity decreases over several orders of magnitude. Depending on the polymer type, percolation threshold can be found between 3 wt% (polypropylene) and 7 wt% CNT (polyethylene). The results for specific resistivity are illustrated in Fig. 2. At a concentration of 6 wt% the specific resistance is low enough to consider the fibers as electrically conductive.

The orientation of CNT plays an important role for the final conductivity, where both plastic deformation of the melt because of the drawing as well as shear forces in the spin plate orient the particles in fiber direction. The influence of the shear rate can be seen when different die diameters are used for extrusion. The results are displayed in Fig. 3.

#### Demonstration of heating

The heating of an as-spun fiber as well as a nonwoven fiber mat can be directly detected with an infrared camera. The results are displayed in Fig. 4. The single fiber can be heated with a difference of about 15 °C to the ambient temperature. This is already enough for applications close to the human body. The temperature of the fiber mat increases even more, since the surface resistance of the whole mat is much lower.

#### Conclusion

It was demonstrated that electrically conductive fibers can be directly melt spun. Therefore, electrical conductivity can be con-


trolled by adding different CNT concentrations. The fibers are usable for heating elements, where the temperature (up to a difference of 15 °C for single fibers) can be controlled by the voltage applied to single fibers or textile fabrics. Possible applications of these heating fibers are seat heaters in vehicles. Conductive fibers with textile properties can be placed closer to the passenger

and help reduce the power consumption of seat heaters.

#### References


- [1] Mai, Y.; Yu, Z.: Polymer Nanocomposites. Cambridge: Woodhead (2006)
- [2] Grady, B.: Carbon Nanotube Polymer Composites. Hoboken: Wiley (2011)
- [3] Alig, I.; Pötschke, P.; Pegel, S.; Dudkin, S.; Lellinger, D.: Plastic composites containing carbon nanotubes: Optimisation of processing conditions and properties. Rubber Fibre Plastics 3 (2011) 92-95
- [4] Wescott, J.; Kung, P.; Maiti, A.: Conductivity of carbon nanotube polymer composites. Applied Physics Letters 90 (2006)
- [5] Skrifvars, M.; Soroudi, A.: Melt Spinning of Carbon Nanotube Modified Polypropylene for Electrically Conducting Nanocomposite Fibers. Solid State Phenomena 151 (2009) 43-47
- [6] Lee, S.; Kim, M.; Kim, S.; Youn, J.: Rheological and electrical properties of polypropylene/MWCNT composites prepared with MWCNT masterbatch chips. European Polymer Journal 44 (2008) 1620-1630
- [7] Steinmann, W. et al.: Melt spinning of electrically conductive bicomponent fibres: structure and electrical properties, Proceedings of 11<sup>th</sup> World Textile Conference AUTEX 2011, Adolphe, D. (Ed.) 716-721, ISBN 978-2-7466-2858-8, Mulhouse/France, June 2011

## SPINNING COMPONENTS

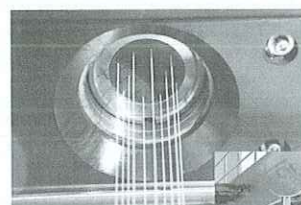

Designed by **MOVE**engineering

PA6  
PA6.6  
PET  
PP

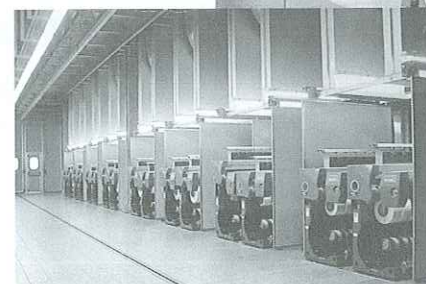

For  
POY  
FDY  
HTY  
BCF  
STAPLE

Manufactured by

**PRINCO** Srl

24020 PARRE (Bg) - Italia - Via Campignano, 6  
Tel. +39(0)35-703688- Fax +39(0)35-703689  
princo@moven.it